


Industeel

Creusabro® 6400



Creusabro® 6400 : the best combination between wear resistance and formability

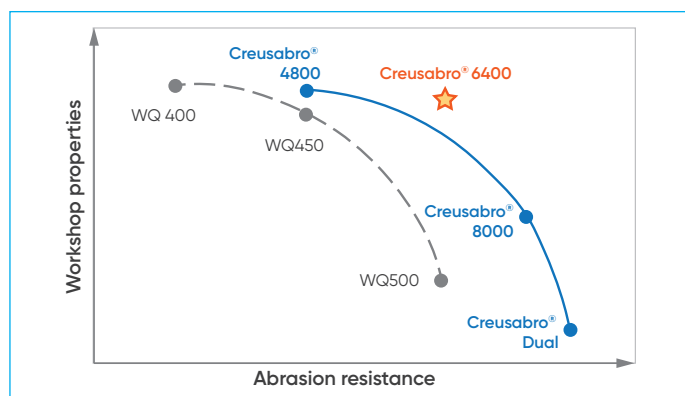

Creusabro® 6400 has been developed to meet all situation where improved wear resistance is required compared to classical 450/ 500 HB martensitic plates, without compromise on toughness, formability and easy processability in the workshop.

Metallurgical concept

Besides the 4800 and 8000 grades, **Creusabro® 6400** is genuinely different than classical low alloyed martensitic abrasion resistant plates. The original chemical composition and the soft quenching rates used in the mill fabrication process develop a uniform through-hardened plate having a multiphase microstructure with retained austenite. This unique metallurgical combination enhances the capacity of surface exposed to wear to increase its hardness up to +70 HB under the action of local plastic deformations caused by impact with rocks or pressure by the abrasive particles. This is known as TRIP-effect (Transformation Induced Plasticity).

Properties

Standards

Creusabro® 6400 is a proprietary grade and registered trademark developed by Industeel. There exists no product standard plates intended for wear resistant applications.

Chemical Analysis - Ladle analysis in weight % (Max. values).

C	S	P	Mn	Ni	Cr	Mo
≤ 0.22	≤ 0.003	≤ 0.02	≤ 4.2	≤ 0.25	≤ 0.25	≤ 0.2

Mechanical Properties


	Hardness (HBW)	Tensile properties			CVN-impact longitudinal -20°C
		YS 0.2% (MPa)	UTS (MPa)	Total Elong. (%)	
Typical	460 ⁽²⁾ → 530 ⁽³⁾	1000	1450	12	40
Specification	425 – 490 ⁽¹⁾	-	-	-	> 27 ⁽⁴⁾

(1) HBW Brinell hardness measured according to ASTM A370, on a milled or ground surface below the decarburized layer typically 0,2–3 mm depending on plate thickness; (2) as-delivered; (3) after work-hardening; (4) for plates up to 30 mm only. Impact testing not performed by the manufacturer; no test value reported in the mill certificate.

Bending properties

For plates up to t = 20 mm, recommended minimum bending radius and die opening are summarized in the following table.

	Min Internal bending radius	Min die opening
Perpendicular to the plate rolling direction	3.25 t	12 t
Parallel to the plate rolling direction	3.5 t	14 t

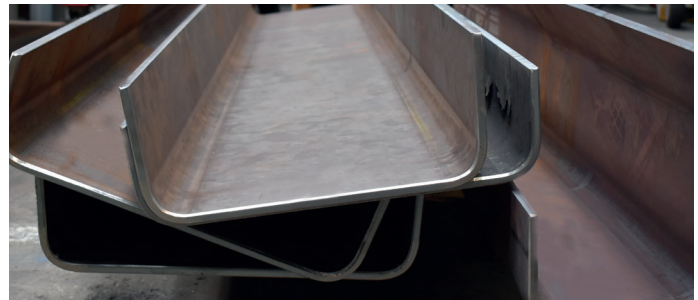

Dimensional program

The thicknesses range of **Creusabro® 6400** extends from 5 to 100 mm, available from standard plate sizes, typically 6000, 8000 or 12000 mm long and 2000 or 2500 mm width. Tailored dimensions are available upon inquiry within the limits given in the following table.

Thickness (mm)			Min Width (mm)	Max Width (mm)	Min Length (mm)	Max Length (mm)	Max unit plate weight (t)
5	to	5.99	1200	2 000	4 000	13 000	12.5
6	to	8.99		2 500			
9	to	11.99		3 100			
12	to	24.99		3 800		14 000	
25	to	40	1500	3 800	3 000	10 000	20
41	to	100		3 000			

Delivery conditions

Creusabro® 6400 is supplied in the “as-quenched” condition.

The plates are produced by low CO2 process in Belgium and France from electric arc furnace, ladle refining and vacuum degassing. The use of scrap recycling and medium manganese content instead of expensive alloying elements such as molybdenum or nickel contribute to reducing the consumption of energy and critical raw materials.

Your contacts

Gilles Hauden

Gilles.Hauden@arcelormittal.com

Industeel France

Le Creusot Plant

56 rue Clemenceau

F - 71202 Le Creusot Cedex

<https://industeel.arcelormittal.com>

Technical data and information are to the best of our knowledge at the time of editing. However, they may be subject to some slight variations due to our ongoing research programme on steels. Therefore, we suggest that information be verified at time of enquiry or order. Furthermore, in service, real conditions are specific for each application. The data presented here are only for the purpose of description, and considered as guarantees when written formal approval has been delivered by our company. Further information may be obtained from the address opposite.